



## Modeling of Zinc production with optimization

Amin Ahmadpour<sup>a, \*</sup>

<sup>a</sup> National Petrochemical Company, Research and Technology Company, Iran

### ARTICLE INFO

#### Article history:

Received  
Received in revised form  
Accepted  
Available online

#### Keywords:

Energy - modeling  
Zinc  
Electrical treatment  
Electrovinning

### ABSTRACT

Zinc is white, bluish or silver metal, very soft which is brittle in normal temperatures, easily breaks with hammer blows and could not be roll in ambient temperatures and could easily roll into sheets at 100- 150 degrees centigrade. Considering the importance of electrical energy consumption in electrical refining processes, electrovinning, its great effect on production cost and other products parameters, including zinc and modeling process with SPSS software that have high credit grade model result, respectively. In this study, by using test equipment indicated that rising temperature causes reduce efficiency and increase consumed energy, and the most optimal flow density value for this process is 2400-300 A/m and electrolyte solution optimum concentration as: 60-50 zinc 140-120 Sulfuric acid, 200ppm manganese sulfate, 500ppm permanganate and gum are 500ppm. Also, energy consumption in Iran's zinc production industry is 4.5 and in developed countries industry is 3.3 . In this study, consumption energy reduced to 2.75 , which, reduction in energy consumption is about 17 percent of advanced industrial countries and about 40 percent of Iran's industry.

### 1. Introduction

Hardness and strength of pure zinc is higher than tin and lead but is lower than aluminum and copper. In such places that tensions occurred into metal, zinc should not be used because zinc shows a little resistance on creeps. Consumption of this metal is function of its plasticity. When this metal alloyed with 4 percent aluminum, strength and hardness resistance increase significantly. Such alloys have casting capabilities especially pressure casting is common. Other casting ways are less consumption. Zinc with high elasticity properties has very good plasticity [1-4]. Zinc electro negativity property causes widespread use it on dry batteries. Zinc important technical property in industry is its very good coverage protection against corrosion [5-8]. Also warm and thick Sulfuric acid will effect on zinc and reacts SO<sub>2</sub> gas. Zinc salts Reactivity on other compounds like: alkaline carbonate, BASICITY phosphate, ammonia, ammonium carbonate, sulfide ammonium and cyanide potassium could note. Zinc industry Production base on hydro mythology method obtained zinc sulfate solution after acid dissolution stage [9-14]. Concentrations measured on this solution done with complex metric titration method and disodium salt EDTA standard

solution. Amine tetra-acetic acid ethylene (EDTA) is an amino acid is insoluble in water so used sodium salt solution which is soluble in water [15-19]. Zinc produced in variety business forms, including ingot, lump, sheet, wire bulleted lists, bar, Cornish and Polk. Compounds and alloys of zinc in the most cases prepared form above forms or scrap containing zinc or in some cases directly from zinc concentrate [20, 24]. Zinc properties in terms of applications have been various uses including: Reactivity with iron, corrosion resistance, electrochemical, low melting point, fluidity, the capacity for curing level; strength; alloy ability, Plasticity, high tensile strength, be nutritional, recovery and heal. Including cover for metals to prevent corrosion, such as: construction and use of instruments, accessories and furniture, automotive, ship building etc [25-29]. to dicasting and casting equipment for consumption in heavy vehicles, accessories and furniture home, toys, tools, etc. to the alloy used in construction and building instruments, automotive equipment, electrical accessories, etc. for consumption in the battery making cars, computers, medical equipment, consumer products and components etc. and various use in industries, such as rubber, pigment, ceramic enamels, paper, food industry, livestock, fertilizers, pharmaceutical industry,

\* Corresponding author. e-mail: aminahmadpour18@gmail.com


cosmetics industry and many other applications include [30-34]. A specialized branch of extractive metallurgy related to metal ore recovery, the concentrate and other intermediate products metallurgy method "wet" is Hydro metallurgy. Leaching, treatment; high grade solution, and finally metal recovery solution are different stages of Hydro metallurgy operation [35-40]. In zinc hydro metallurgy sulfate the goal is producing net zinc that ultimately used for produced net zinc recovery with Electrovining method (Electro-metallurgy process). Electro-metallurgy is a specialized branch of Extractive metallurgy that placed use of electro-chemical methods in extracting metals studied. In this knowledge to achieve process objectives, two types of reaction, i.e. establishing spontaneous flow and utilizing external potential will be operating [41-47]. An advantage of using electrical energy to promote chemical reaction is that the electric force makes no unwanted impurities inside the cell [48-53]. Electrovining is producing a metal from molten salt electrolytes or its aqueous solution with using general electricity. Common name for this operation is electrolysis. Many metals, including zinc, can retrieve by electrolysis in cathode of a cell [54-59].

**2. Article Details**

Materials required for testing this process are: Sulfuric acid 98%, zinc sulfate M = 287.54, distilled water, a distillation of Arabic gum and permanganate and one gram per liter iron sulfate solution. Equipment used in this experiment are Aluminum and lead sheets with dimensions of 5 \* 8 cm, copper bars, balance digital rectifier current (Rectifiers), Multi meters, wire, bashers 600 CC , and one-liter and 250 ml balloons, stopwatch, Pithy 10, 25 and 100 cc . The following results are obtained in different tests:


**2-1. Effect of Sulfuric acid concentration on efficiency and energy consumption**

With assessment figure 1 and 2 indicate that by increasing acid concentration, efficiency decrease and energy consumption increases. Also in figure 1,

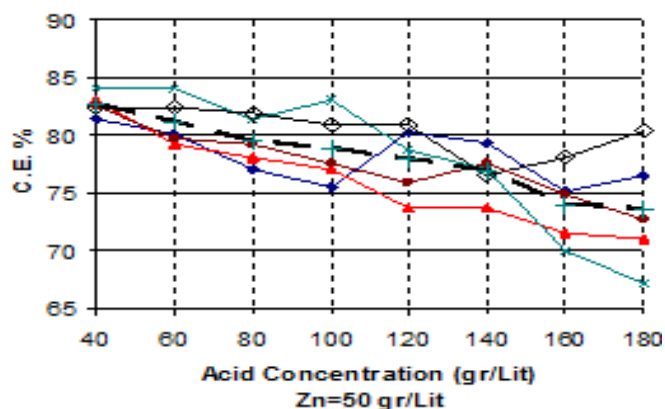

**Figure 1.** Flow efficiency changes according to changes in acid concentration


efficiency decreased with lower slope till acid concentrations 140 gr/lit and after that efficiency decreased with more slope. Due to high acid concentration about 140 gr/lit , Leaching operations in the electrolysis process is required.

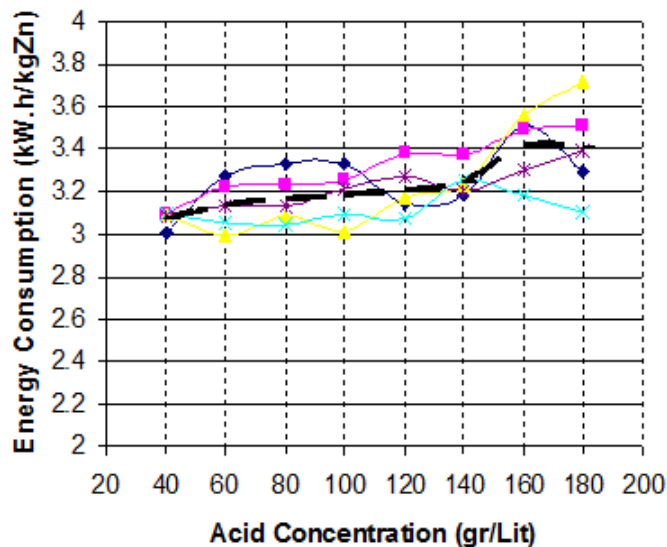

**Figure 2.** Energy consumption changes according to changes in acid concentration

**2-2. Effect of concentration on efficiency and energy consumption**

According to figures 3 and 4 is specified that with more zinc concentration, efficiency is larger and less energy consumption needed.

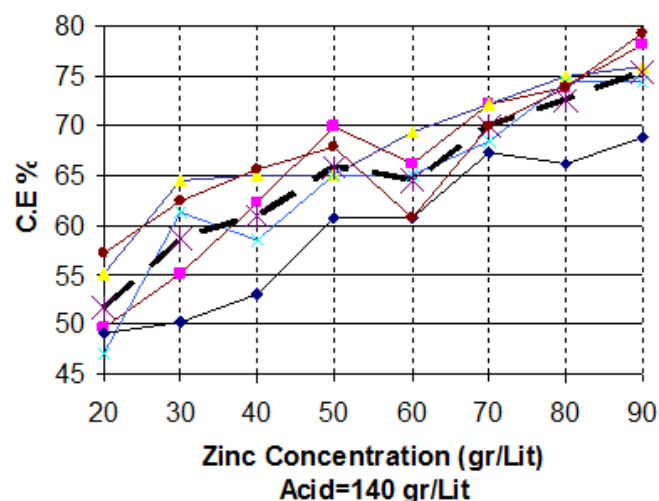

**Figure 3.** Flow efficiency changes according to changes in zinc concentration

The relevant figures, if zinc concentration is less than 50 gr/lit , energy consumption rate increased. Relevant diagrams show that till zinc concentration is 50 gr/lit ,

efficiency increased and at concentration about 50 to 60  $gr/lit$ , efficiency decreased and at concentration more than 60  $gr/lit$ , efficiency again increased and for energy consumption is vice versa of efficiency.

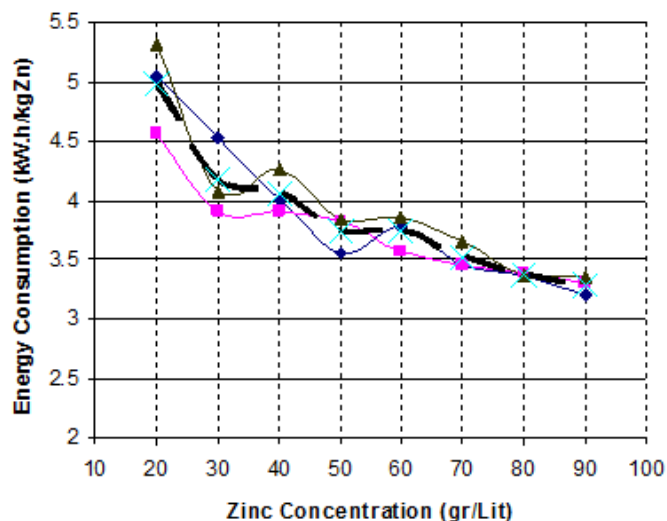


Figure 4. Energy consumption changes according to changes in zinc concentration

### 2-2. Effect of Arabic gum concentration on efficiency and energy consumption

In figure 5, when the gum concentration is between zero to 50  $gr/lit$  efficiency reduction and increasing in energy consumption rate is not high but at gum concentration between 50  $gr/lit$  to 100  $gr/lit$  this rate increased and at concentration between 100  $gr/lit$  to 200  $gr/lit$ , curve's

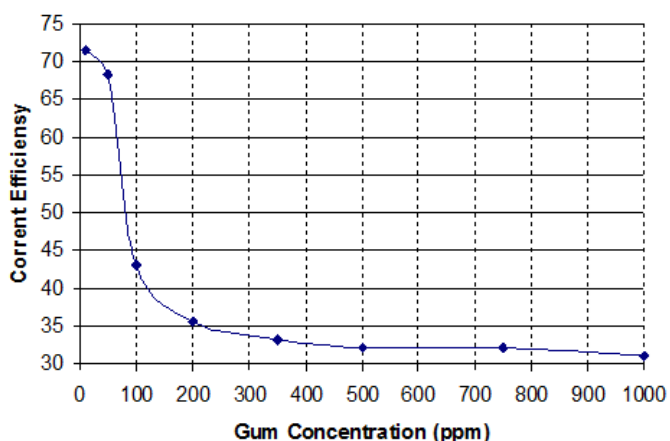


Figure 5. Flow efficiency changes according to changes in gum concentration

slope reduced that at concentrations more than 300, curve slope remains almost constant. Figures 5 and 6 indicate that suitable concentration of gum is 10-50ppm.

Also gum improved zinc structure and changed zinc sediment structure into of a conglomerate or dendrite and makes uniform and continuous zinc precipitation, but if gums concentration rose in electrolyte solution, efficiency reduced and energy consumption increased.

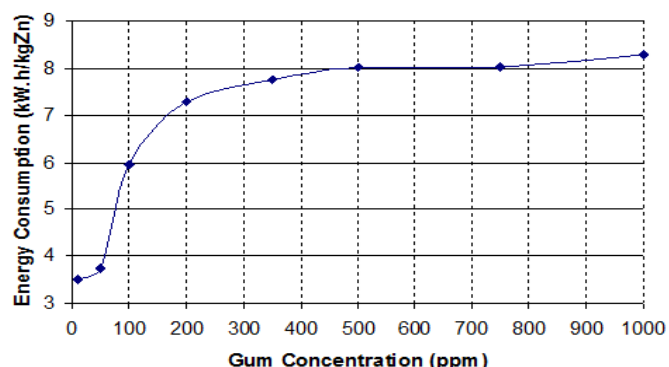


Figure 6. Energy consumption changes according to changes in gum concentration

### 2-3. Effect of manganese sulfate concentration on efficiency and energy consumption

Study on figures 7 and 8 indicate that efficiency at 500ppm permanganate is more than when 35ppm permanganate.

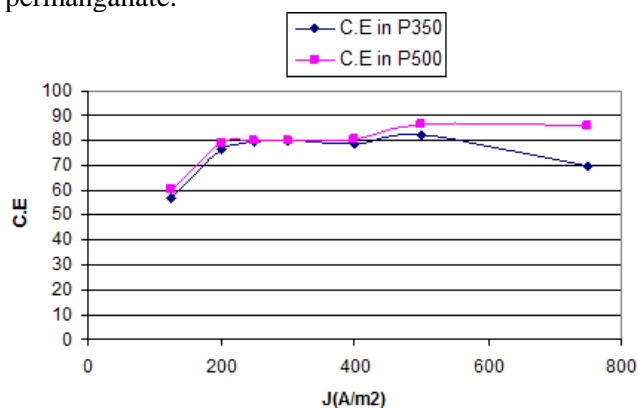


Figure 7. Efficiency changes per flow density in different permanganate concentration on 50 g/l and 140 g/l acid

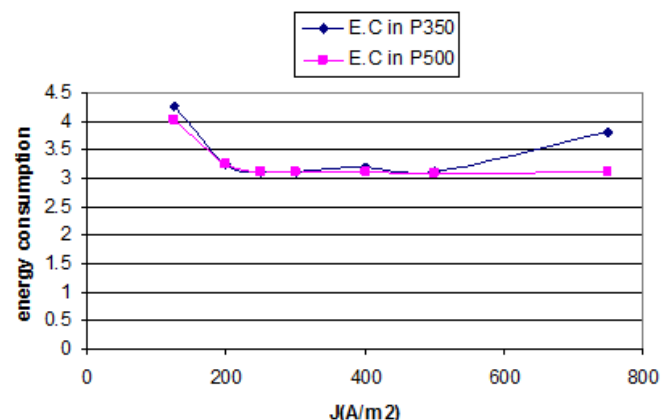


Figure 8. Energy consumption changes per flow density in different permanganate concentration on 50 g/l and 140 g/l acid

Also increase in current density causes increase in efficiency and reduce in energy consumption. In addition, with increasing current density more than 500, efficiency decreases. The highest efficiency reached at 50ppm.

### 3. SPSS software Modeling

In this study, relationship between changes in energy consumption, acid concentration, zinc, gum, permanganate, iron, flow, temperature and efficiency with SPSS software investigated. Obtained model diagnosis coefficient is 97% which validated research is successful. Obtained model is as follows:

$$Y = 1.843 \times 10^{-5} [(x_2)^2 \times Ln(x_2)^2] - 3.44 \times 10^{-4} [(x_7)^2 (Ln(x_2))^2] + 6.6 \times 10^{-5} [x_1]^2 - 0.875 [Ln(x_1)^2] + 1.839 \times 10^{-3} [x_3] - 0.644 [\sqrt{x_4}] - 0.864 [\sqrt{x_5}] + 0.436 [\sqrt{x_5}] - 0.684 [Ln(x_3)] + 1.781 \times 10^{-3} [(x_7)^2 (Ln(x_2))] - 0.183 (x_7) + 42.3$$

X1: Acid, X2: zinc, X3: flow, X4: gum, X5: permanganate, X6: iron, X: 7 temperatures, X8: efficiency

### 4. Conclusion

1- According to acid concentration per energy and acid concentration per efficiency figures, determined that with increasing in acid concentration, efficiency decrease and energy consumption increase.

2- According to zinc sulfate per energy figures indicate that with increasing zinc concentrations to 50  $\frac{gr}{lit}$ , efficiency increased but at concentration more than 50  $\frac{gr}{lit}$ , efficiency reduced with partial energy increasing. Therefore, concentration more than 50  $\frac{gr}{lit}$  is useless and harmful.

3- Adding gum improved operating structure and changing sediment structure from dendrite to clog and cause zinc to deposit uniformly but if more electrolytes solution added, efficiency reduce and energy consumption increase. Gum effect figures shows efficiency reduction. In this figure, if gum concentration increases more than 50ppm the efficiency reduced intensity and at gum concentration more than 150ppm efficiency remains almost constant but gum with low permanganate concentrations can be increased efficiency partially.

4- Low manganese sulfate concentrations causes partial efficiency increase rate. This partial increased (a rate of about 7%) shows at 200ppm concentration.

However, in this process energy consumption increased so efficiency increasing is useless. Increased manganese sulfate causes sediment separated from aluminum sheet surface easier.

5- Gum makes some complex reactions with impurities in solution and may cause changes in the efficiency or energy consumption. Adding 200ppm manganese sulfate to electrolyte solution with 10-2000ppm gum will reduce efficiency, but when only gum added to solution, efficiency is more. It observed that with increasing gum concentration more than 50ppm, flow efficiency decreases and at concentration more than 200ppm, efficiency remains almost constant.

6- Permanganate cause separate deposition easier from aluminum surface and figures show that an increase in permanganate concentration (about 350ppm) causes efficiency partial increased (approximately 5 percent), but it remains nearly constant at higher permanganate concentration. At 200ppm efficiency decrease and energy consumption increased which should be avoiding extract at this concentration. Permanganate critical point was considered 350ppm.

7- At ppm100 gum with presence of permanganate a partial increase at gum concentration causes efficiency reduced and energy consumption increased so combination of 350ppm permanganate with 100ppm gum is recommended.

8- Turbulence: experiments conducted at 120 and 160 acid concentrations (20 more acid and less than the critical point 140). Showed that turbulence can increase efficiency and reduce energy consumption in addition sediment got denser structure.

9- Increased iron II (sulfate) concentration till 100ppm is ineffective but at more concentration decrease efficiency and increase energy so iron II (sulfate) concentration should not be more than 100ppm.

10- Flow density: flow density increased with the increase of flow from 0.25 Amp to 1.5 Amp at fixed level and results that with of the increase flow density from 125 to 300A/m<sup>2</sup> efficiency is increased greatly and reaches about% 50 and energy consumption reduced. Increasing flow density to more than 750A/m<sup>2</sup> increased efficiency but at flow density from 400 to 750 A/m<sup>2</sup> efficiency increase only d 10%.

Flow density causes increased efficiency first from 125 to 300 A/m<sup>2</sup> with high rate and from 300 to 750 A/m<sup>2</sup> increased with lower rate and will not reach more than one extent point. At 125A/m<sup>2</sup> a maximum density at 50 is clearly visible that shows the correct zinc selected concentration is 50gr/lit-1.

Increasing flow density in the solution containing permanganate indicates that the efficiency till 350 increase intensity but with increasing flow density,

increasing efficiency reduced is low and at 750A/m<sup>2</sup>, efficiency decrease with increasing energy consumption.

With increasing flow density, energy consumption decreased regularly from 125 to 250 with high intensity and then from 250 to 750 decreases with lower intensity. With increasing flow density, increasing energy consumption reduces and efficiency increase.

Flow density test contains in solution 350ppm permanganate / 50 zinc / 100ppm acid on two concentrations of Arabic gum 140 and 50ppm showed that increasing flow density to 250A/m<sup>2</sup> efficiency increased with high intensity and reduces energy consumption, but at flows more than This amount, increasing efficiency is high while for 125 to 250 A/m<sup>2</sup> for the solution increased efficiency is 45%. Energy consumption rate decrease lower after 250 A/m<sup>2</sup> that indicates optimal electrolytes solution is 140 acid, 50 salt, 350ppm permanganate, 100 and 50ppm gum concentrations and 500A/m<sup>2</sup>flow density.

11- Temperature Effect: temperature rise from 25 to 80 causes reduced efficiency and increased energy consumption. Graphs of 120, 140 and 160 acid concentrations in temperatures 40, 60 and 80 were compared with 25 .curves indicate that temperature rise is harmful agent. At 80 and 60 , zinc sediment samples were crystallized and at 80 were more which indicates that Crystal sediment growth with temperature and in 80 , sediment formation was completely dendrite which reduced efficiency.

Because of evaporation at high temperature, solution volume reduces so experiments accuracy is not high and results accurate of 80 are less than 60, but which reduce efficiency.

Rising temperature at permanganate solution reduces efficiency and increase energy consumption. At 80 efficiency increased and energy consumption reduced which do not use.

In 350ppm permanganate solution containing gum 50 and 100ppm was observed with increasing temperature, efficiency decreased and energy consumption increased but at 80 efficiency increased and energy consumption decreased that indicates ambient temperature is suitable condition for tests.

## References

- [1] A. Ahmadpour, A. Haghghiasl, and N. Fallah. Investigation of spent caustic wastewater treatment through response surface methodology and artificial neural network in a photocatalytic reactor. *Iranian Journal of Chemical Engineering (IJChE)* 15.1 (2018) 46-72.
- [2] A. Bozorgian, and M. Ghazinezhad, A case study on causes of scale formation-induced damage in boiler tubes. *J. Biochem. Tech.*, 2, (2018) 149-153.
- [3] .A. Haghghiasl A. Ahmadpour,, and N. Fallah. "Photocatalytic treatment of spent caustic wastewater in petrochemical industries." *Advances in Environmental Technology* 2.3 (2017): 153-168.
- [4] A. Bozorgian, Provide an Approach to Reduce Computations in Power System Stability, *Journal of Engineering in Industrial Research*, 3 (2022), 25-33.
- [5] A. Samimi, K. Kavosi, S. Zarinabadi, A. Bozorgian, Optimization of the Gasoline Production Plant in order to Increase Feed, *Progress in Chemical and Biochemical Research* ,3 (2020), 7-19.
- [6] A. Bozorgian, Investigation and Possibility of Applying Gas Injection Method to Increase Pressure in Well A in one of the South Iranian Oil Fields, *International Journal of New Chemistry*, 9 (2022), 1-13.
- [7] A. Samimi, A. Bozorgian, M. Samimi, An Analysis of Risk Management in Financial Markets and Its Effects, *Journal of Engineering in Industrial Research*, 3 (2022), 1-7
- [8] A. Bozorgian, Exergy Analysis for Evaluation of Energy Consumptions in Hydrocarbon Plants, *International Journal of New Chemistry*, 8 (2021), 329-344.
- [9] S. Rezaniasa, S. Mahdunia, B. Oryani, J. Cho, EE. Kwon, A. Bozorgian, H. Rashidi Nodeh, N. Darajeh, and K. Mehranzamir. Biodiesel production from wild mustard (*Sinapis Arvensis*) seed oil using a novel heterogeneous catalyst of LaTiO<sub>3</sub> nanoparticles. *Fuel* 307 (2022), 121759.
- [10] A. Bozorgian, A review of Investigation of the Formation Kinetics of TBAC-like Clathrate Dual Hydrates, *Journal of Chemical Reviews* ,3 (2021), 109-120.
- [11] A. Ahmadpour, A. Bozorgian, Manufacture of Modified Protective Coating Derived from Coal Industry, *Journal of Science and Technology Research*, 1 (2021), 28-39.
- [12] A. Bozorgian, Thermodynamic Modeling of Gaseous Hydrates, *Journal of Engineering in Industrial Research*, 2 (2021), 194-201.
- [13] A. Bozorgian, An Overview of Methane Gas Hydrate Formation, *Journal of Engineering in Industrial Research*, 2 (2021), 166-177.
- [14] A. Samimi, S. Zarinabadi, A. Bozorgian, Optimization of Corrosion Information in Oil and Gas Wells Using Electrochemical Experiments, *International Journal of New Chemistry*, 8 (2021), 149-163.
- [15] A. Bozorgian, Investigation of Clathrite-Like Hydrates in the Gas Phase, *Journal of Engineering in Industrial Research*, 2 (2021), 90-94.
- [16] B. Raei, A. Bozorgian, Thermodynamic Modeling and Phase Prediction for Binary System Dinitrogen Monoxide and Propane, *Journal of Chemistry Letters*, 1 (2021), 143-148.
- [17] A. Bozorgian, Possibility of Using Gas Injection Method for Increasing Pressure in Well A: the Case of Oil Fields in Southern Iran, *Progress in Chemical and Biochemical Research*, 4 (2021), 207-219.
- [18] M. Bagheri Sadr, A. Bozorgian, An Overview of Gas Overflow in Gaseous Hydrates, *Journal of Chemical Reviews*, 3 (2021), 66-82.
- [19] B. Ganavati, V. A. Kukareko, L. S. Tsybul'Skaya, and S. S. Perevoznikov. "Structural state and tribological properties of Co-P coatings." *The Physics of Metals and Metallography*, 115 (2014), 1037-1045

- [20] A. Bozorgian, Investigation of the effect of Zinc Oxide Nano-particles and Cationic Surfactants on Carbon Dioxide Storage capacity, *Advanced Journal of Chemistry, Section B: Natural Products and Medical Chemistry*, 3 (2021), 54-61.
- [21] N. Kayedi, A. Samimi, M. Asgari Bajgirani, A. Bozorgian, Enhanced oxidative desulfurization of model fuel: A comprehensive experimental study, *South African Journal of Chemical Engineering*, 35 (2021), 153-158.
- [22] A. Bozorgian, Investigation of the history of formation of gas hydrates, *Journal of Engineering in Industrial Research*, 1 (2020), 1-18.
- [23] Б. Ганавати, В. А. Кукареко, Л. С. Цыбульская, and С. С. Перевозников. "Структурное состояние и трибологические свойства покрытий Co-P." *Физика металлов и металловедение*, 115 (2014)1100.
- [24] A. Bozorgian, A. Samimi, A review of Kinetics of Hydrate Formation and the Mechanism of the Effect of the inhibitors on it, *International Journal of New Chemistry*, 8 (2020), 41-58.
- [25] A. Bozorgian, Z. Arab Aboosadi, A. Mohammadi, B. Honarvar, A. Azimi, Determination of CO<sub>2</sub> gas hydrates surface tension in the presence of nonionic surfactants and TBAC, *Revue Roumaine de Chimie*, 65 (2020), 1061-1065.
- [26] M. Bagheri sadr, A. Bozorgian, Decomposition of Hydrates in the Pipeline, *International Journal of Advanced Studies in Humanities and Social Science*, 9 (2020), 252-261.
- [27] A. Bozorgian, Investigating the Unknown Abilities of Natural Gas Hydrates, *International Journal of Advanced Studies in Humanities and Social Science*, 9 (2020), 241-251.
- [28] A. Bozorgian, Effect of Additives on Hydrate Formation, *International Journal of Advanced Studies in Humanities and Social Science*, 9 (2020), 229-240.
- [29] A. Bozorgian, Investigation of Well Equipment in the Oil Industry, *International Journal of Advanced Studies in Humanities and Social Science*, 9 (2020), 205-218.
- [30] A. Bozorgian, Z. Arab Aboosadi, A. Mohammadi, B. Honarvar, A. Azimi, Statistical Analysis of the Effects of Aluminum Oxide (Al<sub>2</sub>O<sub>3</sub>) Nanoparticle, TBAC and APG on Storage Capacity of CO<sub>2</sub> Hydrate Formation, *Iranian Journal of Chemistry and Chemical Engineering*, (2020).
- [31] A. Bozorgian, Methods of Predicting Hydrates Formation, *Advanced Journal of Science and Engineering*, 1 (2020), 34-39.
- [32] A. Bozorgian, Z. Arab Aboosadi, A. Mohammadi, B. Honarvar, A. Azimi, Optimization of determination of CO<sub>2</sub> gas hydrates surface tension in the presence of non-ionic surfactants and TBAC, *Eurasian Chemical Communications*, 2 (2020), 420-426.
- [33] A. Bozorgian, Z. Arab Aboosadi, A. Mohammadi, B. Honarvar, A. Azimi, Evaluation of the effect of nonionic surfactants and TBAC on surface tension of CO<sub>2</sub> gas hydrate, *Journal of Chemical and Petroleum Engineering*, 54 (2020), 73-81.
- [34] B. Ghanavati, A. Bozorgian, Removal of Copper II from Industrial Effluent with Beta Zeolite Nanocrystals, *Progress in Chemical and Biochemical Research*, 5 (2022), 53-67.
- [35] A. Bozorgian, Investigation of Hydrate Formation Phenomenon and Hydrate Inhibitors, *Journal of Engineering in Industrial Research*, 1 (2020), 99-110.
- [36] A. Bozorgian, Investigation of Predictive Methods of Gas Hydrate Formation in Natural Gas Transmission Pipelines, *Advanced Journal of Chemistry, Section B*, 2 (2020), 91-101.
- [37] A. Bozorgian, Analysis and simulating recuperator impact on the thermodynamic performance of the combined water-ammonia cycle, *Progress in Chemical and Biochemical Research*, 3 (2020), 169-179.
- [38] A. Bozorgian, Study of the Effect Operational Parameters on the Supercritical Extraction Efficient Related to Sunflower Oil Seeds, *Chemical Review and Letters*, 3 (2020), 94-97.
- [39] В. А. Кукареко, Б. Ганавати, and А. Г. Кононов. "Структура и дюрOMETрические свойства покрытий Ni-P, подвергнутых низкотемпературному отжигу." *Механика машин, механизмов и материалов*, 3 (2014), 59-63.
- [40] A. Bozorgian, S. Zarinabadi, A. Samimi, Preparation of Xanthan Magnetic Biocompatible Nano-Composite for Removal of Ni<sup>2+</sup> from Aqueous Solution, *Chemical Methodologies*, 4 (2020), 477-493.
- [41] J. Mashhadizadeh, A. Bozorgian, A. Azimi, Investigation of the kinetics of formation of Clatrit-like dual hydrates TBAC in the presence of CTAB, *Eurasian Chemical Communication*, 2 (2020), 536-547.
- [42] B. Ghanavati, A. Bozorgian, J. Ghanavati, Removal of Copper (II) Ions from the Effluent by Carbon Nanotubes Modified with Tetrahydrofuran, *Chemical Review and Letters*, 5 (2022), 68-75
- [43] M.E. Bidhendi, Z. Asadi, A. Bozorgian, A. Shahhoseini, M.A. Gabris, New Magnetic Co<sub>3</sub>O<sub>4</sub>/Fe<sub>3</sub>O<sub>4</sub> Doped Polyaniline Nanocomposite for the Effective and Rapid Removal of Nitrate Ions from Ground Water Samples, *Environmental Progress & Sustainable Energy*, (2020).
- [44] A. Pourabadeh, B. Nasrollahzadeh, R. Razavi, A. Bozorgian, M. Najafi, Oxidation of FO and N<sub>2</sub> molecules on the surfaces of metal-adopted boron nitride nanostructures as efficient catalysts, *Journal of Structural Chemistry*, 59 (2018), 1484-1491.
- [45] A. Surendar, A. Bozorgian, A. Maseleno, L.K. Ilyashenko, M. Najafi, Oxidation of toxic gases via GeB<sub>36</sub>N<sub>36</sub> and GeC<sub>72</sub> nanocages as potential catalysts, *Inorganic Chemistry Communications*, 96 (2018), 206-210.
- [46] B. Raei, A. Ghadi, A. Bozorgian, Heat integration of heat exchangers network using pinch technology.(2010) 19th International Congress of Chemical and Process Engineering, *CHISA 2010 and 7th European Congress of Chemical Engineering, ECCE-7*, (2010).

- [47] N. Farhami, A. Bozorgian, Factors affecting selection of tubes of heat exchanger, *Int. Conf. on Chem. and Chem. Process IPCBEE*, 10, 223-228.
- [48] Б. Ганавати, В. А. Кукареко, Л. С. Цыбульская, and С. С. Перевозников. "Структурное состояние и износостойкость покрытий Ni-P." *Современные методы и технологии создания и обработки материалов: Сб. научных трудов. В* (2014): 68-79.
- [49] A. Bozorgian, N.M. Nasab, H. Mirzazadeh, Overall Effect of Nano Clay on the Physical Mechanical Properties of Epoxy Resin, *World Academy of Science, Engineering and Technology International Journal of Materials and Metallurgical Engineering*, (2011).
- [50] A. Bozorgian, N.M. Nasab, A. Memari, Buckling analysis of a five-walled CNT with nonlocal theory, *interaction 1* (2011), 4.
- [51] B. Raei, A. Ghadi, A. Bozorgian, Heat Integration of heat exchangers network using pinch technology, 19th International Congress of Chemical and Process Engineering CHISA, (2010).
- [52] A. Bozorgian, P. KHadiv Parsi, M.A. Mousavian, Experimental Study of Simultaneous Effect of Surfactant and Salt on Drop-Interface Coalescence, *Nashrieh Shimi va Mohandesi Shimi Iran*, 27 (4), 59-68.
- [53] A.H. Tarighaleslami, A. Bozorgian, B. Raei, Application of the exergy analysis in the petroleum refining processes optimization, *The 1st Territorial Chemistry and Industry Symposium, Lecture number: E-1097, Damghan, Iran (in Persian)*. 2009.
- [54] E Parandi, M. Safaripour, M. H.Abdellatif, M. Saidi, A. Bozorgian, Biodiesel production from waste cooking oil using a novel biocatalyst of lipase enzyme immobilized magnetic nanocomposite. *Fuel* 313 (2022) 123057.
- [55] A. Bozorgian, P. Khadiv Parsi, M.A. Mousavian, Simultaneous Effects of Ionic Surfactant and Salt on Drop-Interface Coalescence, *Iranian Journal of Chemical Engineering*, 6 (2009), 73-86.
- [56] A. Bozorgian, The Production of Clay Nano-Composite Epoxy and Comparison of Its Properties with Epoxy Resins, *Journal of Basic and Applied Scientific Research*, 12 (2012), 2923-12929.
- [57] A. Bozorgian, Investigation of Hydrate Formation Kinetics and Mechanism of Effect of Inhibitors on it, a Review, *Journal of Chemical Reviews*, 3 (2021), 50-65.
- [58] A. Bozorgian, Investigation and Comparison of Experimental Data of Ethylene Dichloride Adsorption by Bagasse with Adsorption Isotherm Models, *Chemical Review and Letters*, 3 (2020), 79-85.
- [59] A. Ahmadvpour, A. Bozorgian, A. Eslamimanesh, A.H. Mohammadi, Photocatalytic Treatment of Spontaneous Effluent of Petrochemical Industries by TiO<sub>2</sub> CTAB Synthetic Nanoparticles, *Desalination and Water Treatment*, 249 (2022), 297-308.